
Selection of the cut-off (profile filter) according to ISO 4288:1998 and ISO 3274:1998

The cut-off is selected depending on the workpiece surface either according to the valley spacing or the expected roughness values. At the same time the total evaluation length and the corresponding traverse length are defined according to the standards. Deviations are necessary if the workpiece does not allow the required traverse length. See drawing entries.

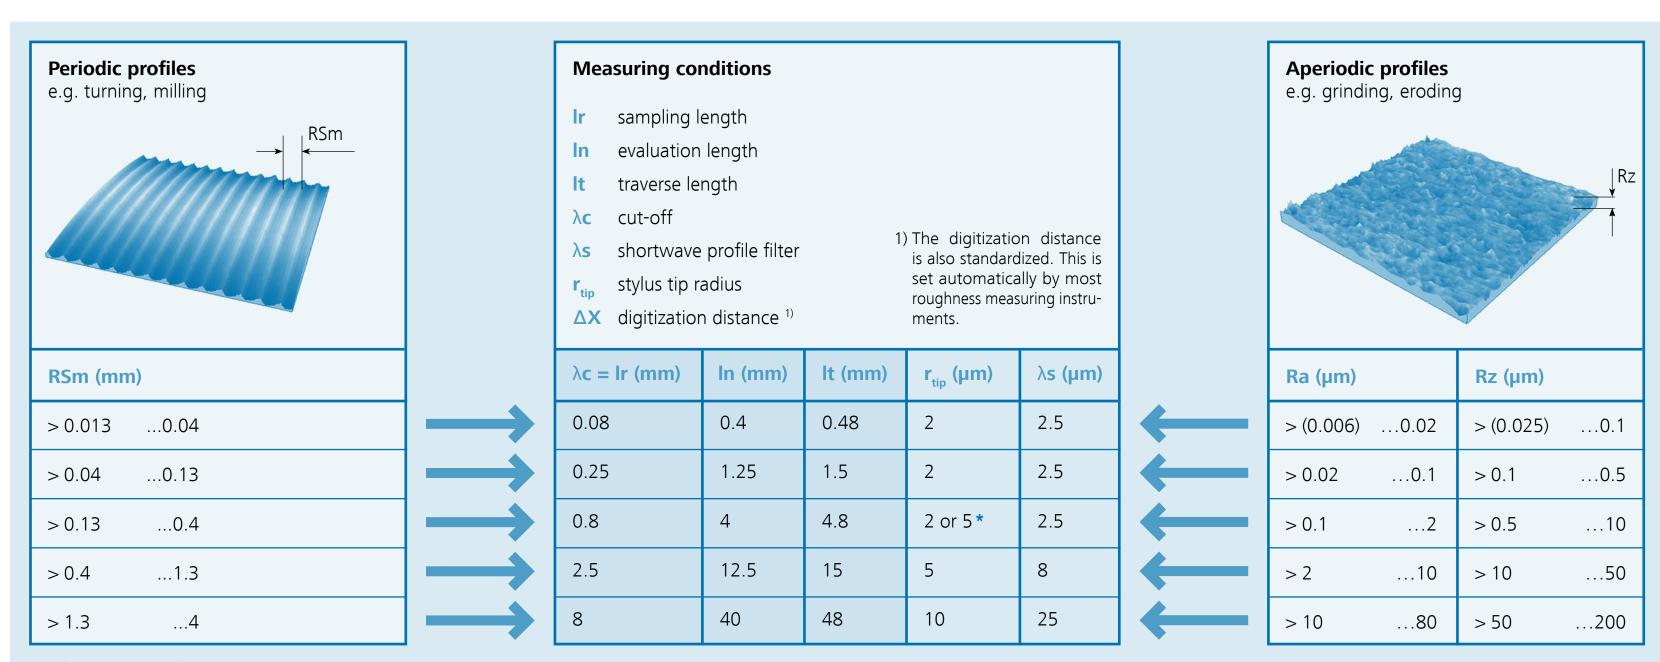

In a periodic profile the mean width of the profile elements RSm is used. With an RSm between 0.4 and 1.3 mm the following measuring conditions result:


 $\lambda c = 2.5 \text{ mm} / \ln = 12.5 \text{ mm} / \ln = 15 \text{ mm} / r_{tin} = 5 \mu \text{m} / \lambda s = 8 \mu \text{m}$.

Shortened standard evaluation length

If the actual possible traverse length on the workpiece surface is not enough for It, the number of sampling lengths is reduced accordingly and specified in the drawing.

If the actually available traverse length is less than a sampling length, the total height of profile Pt of the primary profile is evaluated instead of Rt or Rz.

Division of a surface

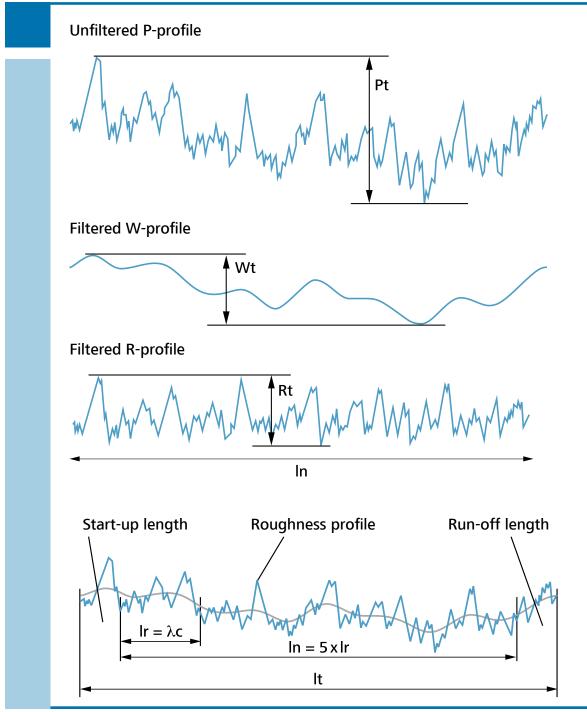

Surface profiles – total height of the profile

The surface profile is measured two-dimensionally using the

The unfiltered primary profile (P-profile) is the actual measured surface profile. Filtering it in accordance with ISO 11562/ISO 16610-21 produces the waviness profile (W-profile) and the roughness profile (R-profile). The variable for determining the limit between waviness and roughness is the cut-off λ c.


Following ISO 4287, all parameter definitions are valid for both the roughness profile as well as for the primary and waviness profiles. The profile type is identified by the capital letters P. R or W.

The total height Pt, Wt or Rt of the respective profile type is the maximum height between the highest peak and the deepest valley of the evaluation length profile.

Evaluation lengths – cut-off

The traverse length (lt) is the total length of the probe movement during the scanning process. It must be greater than the evaluation length in order to be able to form the roughness profile with the profile filter. With the exception of Rt and Rmr(c), the roughness parameters are defined within an evaluation length In, which is determined using an average of five sampling lengths lr.


The sampling length Ir corresponds to the cut-off λc .

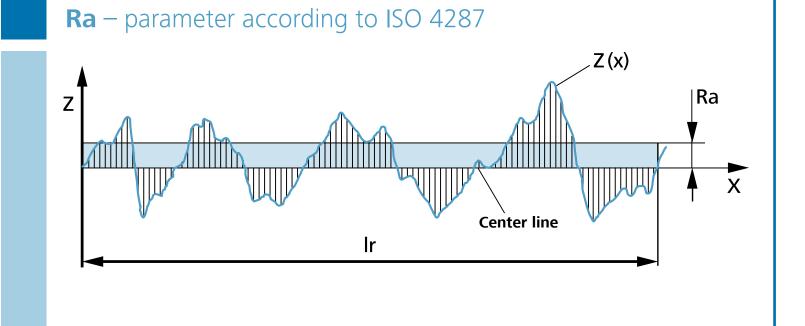

Ra – arithmetical mean deviation of the assessed profile


Ra is the arithmetic mean roughness value from the amounts of all profile values. Ra does not differentiate between peaks and valleys and has therefore a relatively weak information character.

The most important roughness parameters according to ISO 4287, ISO 13565 and EN 10049

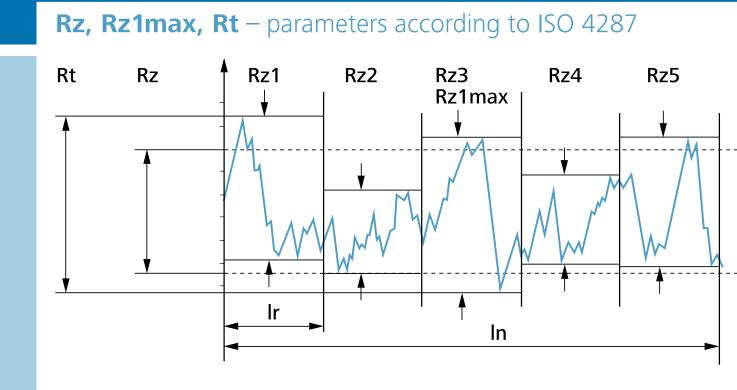


Rz/Rz1max – maximum height of profile: Average value of the five Rz values/greatest Rz value from the five sampling lengths lr.

Rt – total height of profile: Rt is the distance between the highest peak and the deepest valley of the profile of the total evaluation length In.

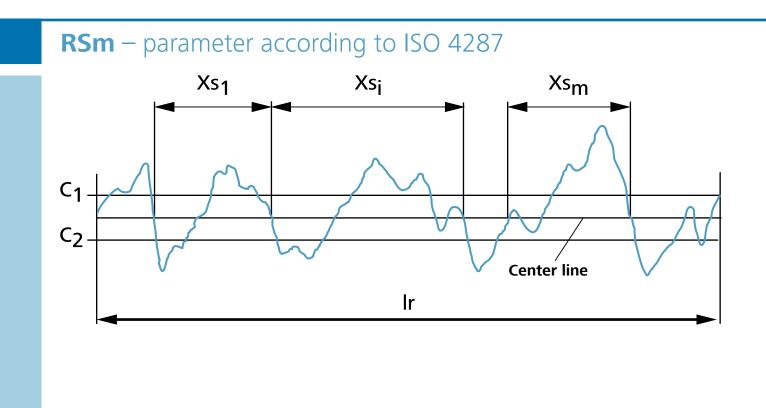

RSm – mean width of the profile elements

RSm is the arithmetic mean value of the width of the roughness profile elements within the sampling length and requires the definition of height discriminations (c1, c2) matching the function of the surface.

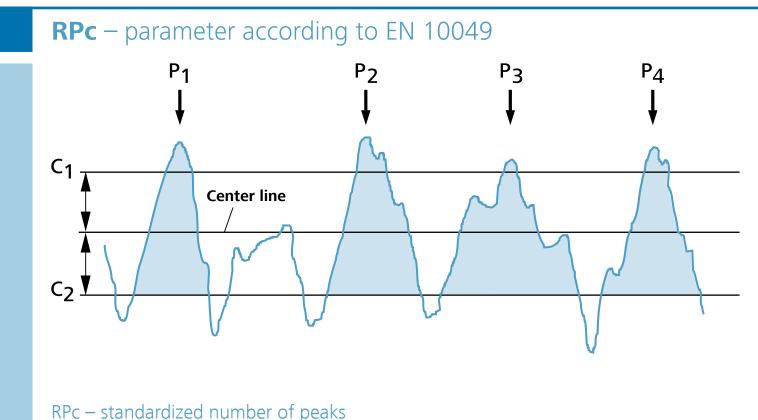



RPc corresponds to the number of local peaks, which successively exceed an upper section line c1 and a lower section line c2. The number of peaks is related to a length of 10 mm irrespective of the evaluation length selected.

Rmr(c) – parameter according to ISO 4287 Reference section height c0 Z(x)Material ratio curve 20¹/₁ 40 60 80 % 100 **Evaluation length In**

Rmr(c) – material ratio of the profile

Rmr indicates what ratio the totaled length in the material has assumed relative to the evaluation length (in %). The comparison is made in the specified section height c and the total evaluation length In. The material ratio curve indicates the material ratio as a function of the section height.

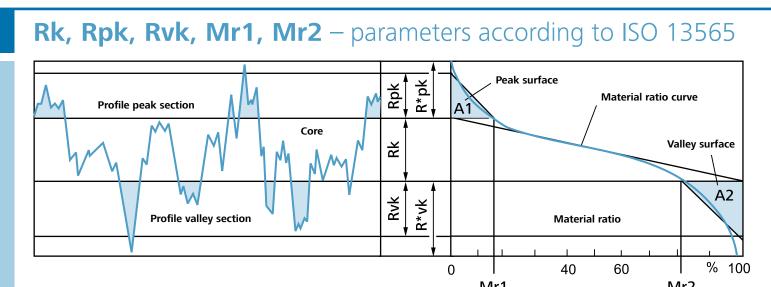

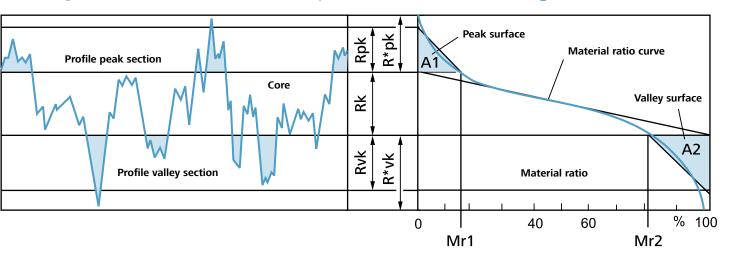

Parameters of the material ratio curve

Rk – core roughness depth

Depth of the roughness core profile.

Rpk – reduced peak height

Mean height of the peaks protruding from the roughness profile.


Rvk – reduced valley depth

The mean depth of the valleys reaching into the material from the core.

Mr1, Mr2 – material ratio

Smallest and greatest material ratio (in %) at the limits of the roughness core area.

Drawing entries according to ISO 1302:2002

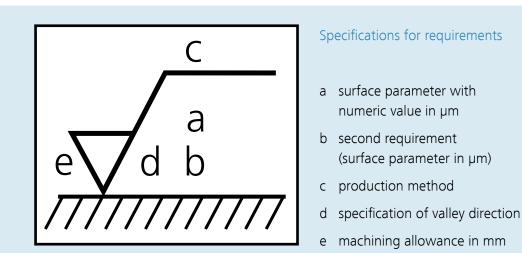

surface parameter with numeric value in µm second requirement (surface parameter in µm) production method

L Rz 2.5 Lower limit value for Rz demanded U Ra 4 L Ra 1

Upper and lower limit value for

Ra demanded

Rzmax 4

The maximum value rule applies $Pt = max. 4 \mu m$

 $Rz = max. 4 \mu m$

2/Pt 4

P-profile, traverse length = 2 mm

Evaluation of measurement results

expected (visual determination).

by the suffix "max", e.g. Rz1max.

the standard ISO 4288:1997.

Special rule VDA

index in the designation.

points is $\leq 0.5 \, \mu \text{m}$.

The use of the λ s filter is prohibited.

Maximum value rule

According to ISO 4288 the surface measurement

should be made where the highest values are to be

The surface is considered good when the measured

values of a parameter do not exceed the fixed maxi-

mum value. In this case, the parameter is identified

If the suffix "max" is not specified, the 16 % rule

applies, which states that the surface is considered

"good" if not more than 16 % of the measured

parameter values exceed the fixed maximum value.

You will find further information about this rule in

The 16 % rule is not used. VDA 2006 assumes that the dispersion of the parameters is taken into account

in the definition of the limit values. The maximum

value rule applies generally even without the "max"

* At Rz \leq 2 µm the stylus tip radius is 2 µm, at Rz > 2

μm it is 5 μm. The distance between two measuring

0.008-2.5/Rz1


Transmission characteristic does not comply with standard case (cf. table). Rz = max. 1 µm WDc 0

WDc0 or WDt 0: no dominant waviness allowed

2.5x5/WDt 2.5

Drawing entries according to VDA 2005 – dominant waviness

In the period range up to 2.5 mm, WDt = max. 2.5 μ m applies

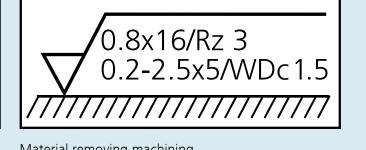

The evaluation length is 12.5 mm and $\lambda c = 0.8$ mm, $Rz = max. 3 \mu m.$ In the period range of 0.2 to 2.5 mm,





 $Rz = min. 2.5 \mu m$

www.jenoptik.com/metrology